

**LEADER CHROME 5 BASIC (E 8015 B6)**

AWS : SFA 5.5, E 8015 B6

**Applications**

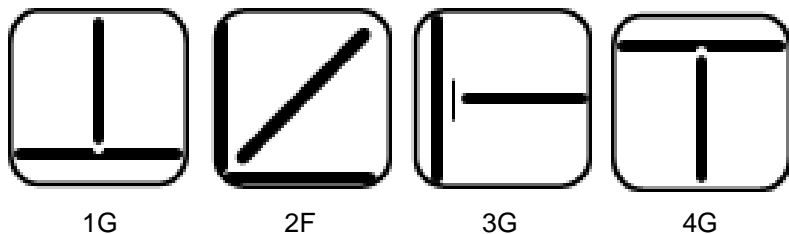
It is used for welding of 5% Cr, 0.5% Mo steel for high temp application in oil refineries. Power plants, Petrochemical plants. Fertilizer Industries.

**Characteristics on Usage**

A low hydrogen iron powder type basic coated all position electrode. It gives weld deposit which has contain 5% Cr, 0.5% Mo for the welding of similar Cr-Mo steel. The weld metal is of radiographic quality and has creep resistance upto 650 °C. Dry the electrode at 300 °C for obtaining best results.

**Notes On Usage**

- 1) Preheat at 150 - 250 °C and postheat at  $690 \pm 14$  °C.
- 2) Dry the electrode at 350-400 °C for 60 Min- before use.

**Welding Positions****Chemical Composition Of Weld Metal**

C%	Mn%	Si%	S%	P%	Cr %	Ni %	Mo %
0.05 - 0.10	1.0 Max	0.90 Max	0.030 Max	0.030 Max	4.0 6.0	0.40 Max	0.45 - 0.65

**Mechanical Properties Of Weld Metal**

(After PWHT at  $740 \pm 15^\circ\text{C}$  for 1 Hr soaking)

U.T.S. (N/mm <sup>2</sup> )	Y.S. (N/mm <sup>2</sup> )	ELONGATION ( L = 4d ) %
550 Min	460 Min	19 % Min

**Packing and Welding Current**

SIZE ( mm )	KG PER PACKET	KG PER CARTON	Current (Amps)	In Amps
2.50 x 350	5	20	DC (+)	60 - 90
3.15 x 350	5	20		100 - 140
4.00 x 350	5	20		140 - 180
5.00 x 350	5	20		190 - 240